

United States
Department of
Agriculture

Forest Service

Technology &
Development
Program

7700—Transportation Systems
April 1999
9977 1201—SDTDC



Asphalt Seal Coat Treatments



Asphalt Seal Coat Treatments

Alan Yamada, P. E.
Civil Engineer

San Dimas Technology and Development Center
San Dimas, California

April 1999

Information contained in this document has been developed for the guidance of employees of the Forest Service, USDA, its contractors, and cooperating Federal and State agencies. The Department of Agriculture assumes no responsibility for the interpretation or use of this information by other than its own employees. The use of trade, firm, or corporation names is for the information and convenience of the reader. Such use does not constitute an official evaluation, conclusion, recommendation, endorsement, or approval of any product or service to the exclusion of others that may be suitable.

The US Department of Agriculture (USDA) prohibits discrimination in all its programs and activities on the basis of race, color, national origin, gender, religion, age, disability, political beliefs, sexual orientation, and marital or family status. (Not all prohibited bases apply to all programs.) Persons with disabilities who require alternative means for communication of program information (Braille, large print, audiotape, etc.) should contact USDA's TARGET Center at 202-720-2600 (voice and TDD).

To file a complaint of discrimination, write USDA, Director, Office of Civil Rights, Room 326-W, Whitten Building, 14th and Independence Avenue, SW, Washington, DC 20250-9410 or call 202-720-5964 (voice or TDD). USDA is an equal opportunity provider and employer.

CONTENTS

INTRODUCTION	1
WHAT'S NEW WITH ASPHALT SEAL COATS?	1
WHY ASPHALT SEAL COATS?	2
WHAT ARE ASPHALT SEAL COATS?	2
WHAT ARE PAVING GRADE ASPHALT CEMENTS, CUTBACK ASPHALTS, AND ASPHALT EMULSIONS?	2
Paving Grade Asphalt Cements	3
Cutback Asphalts	3
Asphalt Emulsions	3
WHAT IS COAL TAR?	5
MODIFICATIONS OF ASPHALT EMULSIONS	5
High Float Asphalt Emulsions	5
Polymer Modified Emulsions	5
Rejuvenating Emulsions	6
TYPES OF ASPHALT SEAL COAT SURFACE TREATMENTS	6
Fog Seal	6
Sand Seal	7
Scrub Seal	8
Chip Seal	9
Multiple Chip Seals	10
Slurry Seal	11
Cape Seal	12
Microsurfacing	12
Pavement Dressing	14
SUMMARY	14
APPENDIX A	17
APPENDIX B	21
APPENDIX C	23

INTRODUCTION

This publication identifies and discusses applications of the various asphalt seal coat treatments that are available. This publication also describes each of the treatments, the methods of application, advantages and disadvantages, expected performance, and costs. Information contained in this publication will provide a general understanding of asphalt seal coats for the apprentice and identify recent developments in the field for the seasoned road manager.

WHAT'S NEW WITH ASPHALT SEAL COATS?

Did you know that:

- High float emulsions are being selected for cold regions to improve chip retention
- Polymer modified asphalt emulsions are improving the performance of the asphalt cement in a variety of environmental conditions, improving durability, and chip retention

- Asphalt emulsions with rejuvenating properties are being used as fog seals and sand seals to restore aged pavements and seal voids and cracks
- The “scrub seal” method, see figure 1, of using a pull broom following the asphalt emulsion distributor truck and the sand spreader eliminates or reduces crack-sealing costs
- Manufactured lightweight aggregates are used to reduce windshield damage caused by loose stones
- Rapid setting low temperature emulsions exhibit better chip retention on pavement temperatures down to 40 °F (4.4 °C)
- Microsurfacing is similar to a slurry seal application but allows a thicker coarse to be applied and allows traffic on the roadway sooner.

Information on these items is described in this publication.



Figure 1—Distributor truck and scrub broom. (Photo courtesy of Western Emulsion.)

WHY ASPHALT SEAL COATS?

Asphalt seal coat treatments are mainly a preventive maintenance procedure applied to the asphalt pavement surface to prevent or delay costly corrective measures (figure 2). Asphalt seal coats are surface treatments designed to seal and protect the asphalt pavement from harmful environmental conditions such as sunlight, rain, and snow. Surface treatments are also applied to enhance the wearing properties and improve the traction between the pavement and vehicle tires.

Asphalt seal coat treatments are surface treatments and will not cure problems beneath the pavement such as a base failure. If the material beneath the asphalt pavement has deteriorated, treating the surface of the pavement will not solve the problem. Surface treatments work well where the distresses are limited to pavement surface deterioration, or where cracks are not severe. The seal coat limits water from infiltrating through the pavement into the underlying material.

WHAT ARE ASPHALT SEAL COATS?

Asphalt seal coats are composed of a thin layer of an asphalt material such as cutbacks, asphalt emulsions, or paving grade asphalt cement. Modifiers are often added to the asphaltic liquid mixture and may include rubber, latex, polymers, and rejuvenators. Sand, aggregate, mineral and synthetic fillers, and rubber crumbs can be applied after the asphaltic mixture is applied to the pavement surface. Some seal coats such as slurry seals and microsurfacing incorporates the sand, aggregate, and fillers in the mixture before placing it on the roadway.

WHAT ARE PAVING GRADE ASPHALT CEMENTS, CUTBACK ASPHALTS, AND ASPHALT EMULSIONS?

The asphalt cement used in road construction and maintenance is one of many products refined from crude oil. In order for the asphalt to be used for road maintenance purposes, it must be fluid to



Figure 2—Asphalt distributor. (Photo courtesy of Asphalt Institute.)

effectively coat the aggregate or be dispersed on the roadway evenly. Heating, dissolving in a petroleum solvent, or emulsifying with water allows the asphalt to become fluid. Table 1 summarizes the uses of asphalt materials for surface treatments.

Paving Grade Asphalt Cements

Paving grade asphalt cements are made fluid by heating and can be sprayed on the road surface. They are graded according to three different systems: viscosity, viscosity after aging, and penetration. The viscosity graded asphalt is denoted by the letters “AC” for “Asphalt Cement” followed by a number. The lower the number, the softer the asphalt cement is. Asphalt cement graded by viscosity after aging is denoted by the letters “AR” for “Aged Residue” followed by a number. Again the lower the number, the softer the asphalt is. A third grading method uses the penetration test to grade the asphalt cement and is denoted by numbers. The numbers relate to the depth of penetration of the asphalt cement by a needle under a specific load. The lower the number, the less distance the needle penetrates, and therefore, the harder the asphalt cement is.

Advantages

The curing time for a paving grade asphalt cement application is fast because as soon as the material cools, it achieves full strength. It is pure asphalt cement without additives such as solvents or emulsifying agents.

Disadvantages

High temperatures (121 to 177 °C [250 to 350 °F]) are required to make the material fluid for construction use. The cover aggregate or sand must be placed immediately before the asphalt cement cools to obtain proper bonding.

Cutback Asphalts

Cutback asphalts are asphalt cements made fluid for construction by the addition of a petroleum solvent such as naphtha, kerosene, or heavy oil. After the liquid material is applied to the road surface, the solvent evaporates, leaving the asphalt cement on the roadway.

The cutback asphalts are graded by curing times, which are denoted by letters; the letters are followed by viscosity-controlled grades, which are denoted by numbers. Rapid-curing (RC), medium-curing (MC), and slow-curing (SC) are the letter designations. A lower grade number following the letter designation indicates that the material includes more solvents and, therefore, is more fluid than a higher grade number. Rapid-curing cutback asphalt is generally not used today because of environmental concerns.

Advantages

Cutback asphalts are applied at cooler temperatures (10 to 121 °C [50 to 250 °F]) than paving grade asphalts. The cutback asphalts penetrate the asphalt pavement better than asphalt emulsions.

Disadvantages

All cutbacks emit hydrocarbons during the evaporation process, which pollute the atmosphere. Cutback asphalts generally cost more than asphalt emulsions. The solvents used in the cutbacks pose a potential fire hazard.

Asphalt Emulsions

Asphalt emulsions use surface-active agents or surfactants to suspend the asphalt particles in water. These surfactants or emulsifying agents are similar to soap allowing the minute asphalt particles and the water to form a uniform mixture. When the asphalt emulsion is applied to the roadway, the asphalt cement and the water separate. This process is called breaking. The water then evaporates leaving the asphalt cement and the emulsifying agents behind.

Asphalt emulsions commonly used in road maintenance operations are either anionic or cationic. The asphalt in the anionic type has a negative electrical charge while the cationic type has a positive electrical charge. Cationic emulsions are denoted by a letter “C” at the beginning of the emulsion type, and the absence of “C” denotes an anionic emulsion. The emulsions are classified by the letters indicating the relative rate of curing. Rapid-setting (RS), medium-setting (MS), slow-

Table 1—Uses of asphalt.

	Asphalt Cements										Asphalt Emulsions										Cutback Asphalts																		
Type of Construction	Viscosity Graded Original					Viscosity Graded Residue					Penetration Graded					Anionic					Cationic					Medium Curing				Slow Curing									
	AC-40	AC-20	AC-10	AC-5	AC-2.5	AR-16000	AR-8000	AR-4000	AR-2000	AR-1000	40-40	60-70	85-100	120-150	200-300	RS-1	RS-2	MS-1	MS-2	MS-2h	HFMS-2h	SS-1	SS-1h	CRS-1	CRS-2	CMS-2	CMS-2h	CSS-1	CSS-1h	30	70	250	800	3000	70	250	800	3000	
Fog Seal																			X			X	X					X	X										
Sand Seal																X	X	X						X	X														
Chip Seal				X	X								X	X	X	X								X	X														
Multiple Chip Seal				X	X								X	X	X	X								X	X														
Slurry Seal																						X	X					X	X										
Cape Seal																X							X		X														
Micro Surfacing																													X										

setting (SS), and quick-setting (QS) are the designations. Emulsions are further classified by a number indicating viscosity (1 is more fluid than 2) and a letter for the hardness of the base asphalt ("h" for a harder grade and "s" for a softer grade). High float emulsions are designated with the letters "HF" preceding the emulsion grades.

Advantages

Asphalt emulsions are applied at cooler temperatures (10 to 66 °C [50 to 150 °F]) than cutback or paving grade asphalts. The water evaporating from the emulsion is environmentally safe. Emulsions can be made with a high viscosity to resist runoff on steeper sideslopes and road grades.

Disadvantages

The asphalt and water in the emulsion may separate under boiling or freezing temperatures. Emulsions are not compatible with cutbacks or paving grade asphalt cements.

WHAT IS COAL TAR?

Coal tar is similar in appearance to asphalt but is produced as a byproduct of bituminous coal during the production of metallurgical coke. Coal tar can be made into an emulsion comparable to asphalt emulsion and applied to asphalt pavement surfaces. Coal tars are used as a surface treatment on roads, driveways, parking lots, gas stations, and airport taxiways.

Advantages

Unlike asphalt cement, coal tar is resistant to damage from gasoline, diesel, oil, salt, and chemicals.

Disadvantages

Coal tar generally costs more than asphalt cement.

MODIFICATIONS OF ASPHALT EMULSIONS

High Float Asphalt Emulsions

High float asphalt emulsions (HFEs) are being used more often today than in the past. Usually

when an emulsion breaks, the remaining emulsifying agent has little effect on the asphalt. This is not so with an HFE. The high float emulsifying agent creates a gel structure in the asphalt residue. The gel structure permits a thicker asphalt coating on the aggregate particles. The thicker film prevents raveling and is more resistant to oxidation from exposure to the atmosphere. The high float residue is resistant to flow at high temperatures while not being affected as much by low temperatures. This allows a softer grade of the base asphalt to be used that will resist bleeding at high temperatures. The softer asphalt does not become as brittle at low temperatures and resists thermal cracking. HFEs are commonly used in hot arid environments with cold evenings.

Polymer Modified Emulsions

Probably the most common modifier to asphalt emulsions is polymer additives. Polymers and polymer combinations are being modified constantly to enhance the various properties of the asphalt cement binder. Polymers can be used for any asphalt seal coat applications.

Polymers generally used in the asphalt industry are either elastomeric (rubber like) or plastomeric (plastic like). The elastomeric polymers increase the elasticity and flexibility of the asphalt cement, while the plastomeric polymers improve the strength and the durability of the asphalt cement. Polymerized asphalt emulsions are effective in improving stone retention when construction conditions are less than ideal such as in low air temperatures, shady areas, or sinuous alignment. Polymers can improve the performance of the asphalt binder in both cold and hot temperatures. Some polymers allow the emulsion to chemically break and do not depend on temperature to separate the asphalt cement from the water within the emulsion. This allows the emulsion to break at lower temperatures and provides a longer construction season in some areas or allows surface treatments to be done at night. Polymer modified binders usually cost more, but they increase the performance of the asphalt cement often reducing life cycle costs.

Rejuvenating Emulsions

As pavement ages, asphalt cement becomes brittle and loses some of the binding qualities. Rejuvenating emulsions penetrate the asphalt pavement, soften the brittle asphalt, and improve the asphalt cement's ability to bind with the aggregate. The rejuvenating agent is also known to heal small cracks in the pavement.

TYPES OF ASPHALT SEAL COAT SURFACE TREATMENTS

This section briefly describes the types of surface treatments available, some of the advantages and disadvantages, equipment used, relative cost, and expected performance. The cost for each treatment will vary considerably depending on the size of the project, location of the project, availability of materials, whether the work is performed by a force account crew or private contractor, amount of traffic control required, and other factors. The life expectancy of the various surface treatments will also vary in the amount of asphalt applied, quantity and quality of the asphalt, quality of the cover material, volume of traffic, alignment of the roadway, temperature extremes, ultraviolet exposure, and the use of chains or studs on vehicle tires. The costs and life expectancy should be used as a general comparison between each surface treatment type.

Fog Seal

A fog seal is an application of asphalt emulsion sprayed onto a pavement surface with or without a sand cover, see figure 3. The emulsion is diluted to the proper consistency in order to get a complete coverage on the roadway but not be too thick to cause a slippery surface. A fog seal works better on a coarse aggregate surface where the asphalt emulsion has room to pond between the aggregate particles. On a smooth aggregate surface, the asphalt rests on the surface covering the top of aggregate particles, creating a slippery surface for the vehicles. If the fog seal was not properly applied and a slippery surface exists, a dry choke cover is applied to the surface. The choke is usually clean sand or aggregate that is less than 6.3 millimeter (0.25 inch) in diameter.

Fog seals are used to delay weathering of the pavement, waterproof the pavement surface, improve the pavement's ability to keep water from penetrating the base course or subgrade, and reduce raveling.

Asphalt emulsions with rejuvenating properties such as GSB-Emulsion Sealer and Rejuvenator supplied by Asphalt Systems, Inc. or Reclamite from Witco Corporation can be used to penetrate, rejuvenate, and seal the surface of asphalt pavements. Reclamite requires a thin layer of sand (0.5 to 1 kilograms/square meter) (1 to 2 pounds/square yard) to be applied before allowing traffic onto the roadway.

Advantages

Fog seals are inexpensive compared to other surface treatments. Only a distributor truck is required to apply the fog seal in most cases.

Disadvantages

The expected life of the fog seal is generally shorter than other surface treatments. If applied too heavily, the fog seal could be slippery and hazardous for the road users.

Equipment

The equipment needed for a fog seal is a distributor truck to dispense the asphalt emulsion and a sand spreader if sand is applied.



Figure 3—Fog seal. (Photo courtesy of Asphalt Institute.)

Application

Fog seals are applied at 0.23 to 0.68 liters/square meter (0.05 to 0.15 gallons/square yard) of the diluted asphalt emulsion.

Cost and life expectancy

Typical costs are \$0.54/square meter (\$0.45/square yard). The expected life of a fog seal is 1 to 3 years.

Sand Seal

A sand seal is a sprayed application of asphalt emulsion followed by a covering of clean sand or fine aggregate, see figure 4. A pneumatic tired roller is often used after applying the sand. Excess sand is removed from the road surface after rolling.

Sand seals enrich weathered pavements and fills fine cracks in the pavement surface. The sand can provide additional skid resistance to the pavement while also inhibiting raveling.

As in fog seals, emulsions with rejuvenating properties can be used. The additional expense of the rejuvenating emulsion could be cost effective if there are many small cracks in the pavement. CRF Restorative Seal of Witco Corporation and GSB-88 of Asphalt Systems, Inc. are products that are designed to penetrate and restore aged pavements.

Advantages

The sand seal generally provides a thicker coating on the pavement surface than the fog seal resulting in a longer life expectancy. The sand seal on polished aggregate surfaces can provide additional skid resistance.

Disadvantages

Only fine cracks are filled and larger cracks tend to reappear within a year.

Equipment

The equipment needed for a sand seal is a distributor truck to dispense the asphalt emulsion



Figure 4—Sand seal. (Photo courtesy of Western Emulsion.)

and a sand spreader to add the sand cover. A pneumatic tire roller can be used but is not required. A broom is used to remove the excess sand.

Application

Emulsified asphalts are applied from 0.45 to 1.13 liters/square meter (0.10 to 0.25 gallons/square yard). The sand is applied at 10 to 13 kilograms/square meter (18 to 25 pounds/square yard) yielding a 4.7-millimeter (3/16-inch)-thick new layer over the existing pavement.

Cost and life expectancy

The typical costs are \$0.84/square meter (\$0.70/square yard). The expected life of a sand seal is 3 to 4 years.

Scrub Seal

The scrub seal process, see figure 5, drags a brooming mechanism over the road surface after the asphalt emulsion has been applied to fill the pavement cracks and voids. A layer of sand or aggregate is applied over the emulsion followed by

another drag broom, forcing the sand into the emulsion filled cracks and voids. A pneumatic tire roller is then used over the seal. The excess sand or aggregate is broomed off the roadway a couple of hours after application depending on weather conditions.

The Arizona Department of Transportation (DOT) has been using the brooms in the scrub seal method since 1985 and tried various asphalt emulsions. In 1989 they tried a polymer modified product called Polymerized Asphalt Surface Sealer (P.A.S.S.)[™] manufactured by Western Emulsions, Inc. and have been using this product yearly since then. California, Nevada, and Arizona DOTs have been using the scrub seal method with P.A.S.S.[™] for the last 5 to 10 years with success. The road superintendents from these states claim they save money and time by reducing or eliminating sealing the cracks prior to applying the asphalt surface treatment. Another advantage of the P.A.S.S.[™] stated by the road superintendents was the forgiving nature of the product that allowed them to place the sand or aggregate 30 minutes after



Figure 5—Scrub seal process. (Photo courtesy of Western Emulsion.)

applying the emulsion. The product also accepts less costly, “dirty” sand or aggregate with fines (minus #200 sieve) usually up to 6 percent of the total weight. The DOTs applied the scrub seal and P.A.S.S.™ on highways and freeways.

Golden Bear Division of Witco Corporation manufactures a product called CRF that also could be used with the scrub seal method.

Advantages

The scrub seal method can fill cracks up to 12.7 millimeter (0.5 inch) wide that would have normally been filled by crack sealing.

Disadvantages

Many contractors are not familiar with the scrub seal method. Tests may be needed to determine what emulsion or polymer modified emulsion would work with the brooms. If using P.A.S.S.™, the product costs more and may not be available at your locale.

Equipment

The equipment is the same as for a chip seal operation with the exception of the brooming mechanism, which is needed after the emulsion is applied and after the aggregate is spread.

Application

Emulsified asphalt is applied from 0.68 to 1.81 liters/square meter (0.15 to 0.40 gallons/square yard). The sand or aggregate is applied at 5.4 to 10.8 kilograms/square meter (10 to 20 pounds/square yard).

Cost and life expectancy

The cost will vary tremendously depending on the type and quantity of emulsion used, but the typical cost is \$1.55/square meter (\$1.30/square yard). The expected life of a scrub seal is 4 to 6 years.

Chip Seal

Chip seals are the most common surface treatment for low volume roads. A chip seal is an application

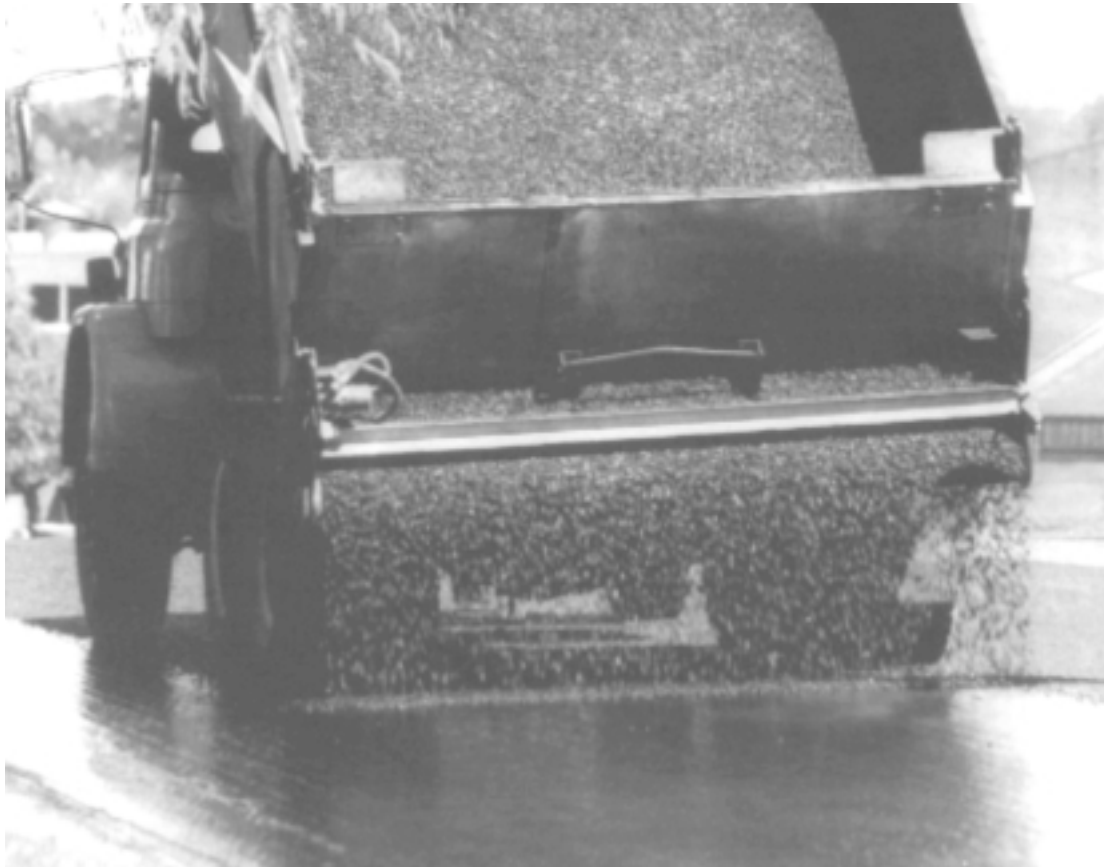


Figure 6—Rock tailgate spreader. (Photo courtesy of Asphalt Institute.)

of asphalt followed by an aggregate cover. The asphalt is usually applied as a hot asphalt cement, cutback asphalt, or emulsified asphalt. After the hot asphalt cement, cutback asphalt, or asphalt emulsion is applied to the pavement surface, aggregate is immediately applied over the asphalt before the hot asphalt cement cools or the asphalt emulsion breaks, see figure 6. A pneumatic roller is used to reorient or seat the aggregate particles and tighten the rock matrix. After the asphalt cures, the excess aggregate is removed by brooming.

A chip seal application corrects raveling and seals small cracks on the old pavement surface while providing a new skid resistant surface. Chip sealing may also be used following crack sealing.

If cracked windshields is a significant problem, then volcanic cinders or manufactured light weight aggregate (LWA) can be used. LWA is manufactured from shale, clay, and slate. These materials are mixed, extruded, and baked in a kiln. Being light in weight, these aggregates have less mass to break a windshield when they become projectiles. The LWA costs more than locally available aggregate and may not be as durable. Reducing loose aggregate and cracked windshields may also be accomplished by using a polymer modified emulsion with higher quality, or smaller sized aggregates.

Also available are rapid-setting, low temperature polymer modified emulsions designed to “chemically” break at temperatures as low as 4.4 °C (40 °F) and rising. This type of emulsion would be useful for roads located at high elevations or other areas where the temperatures are lower. The emulsion can also be used where the roads are constantly in the shade.

Crumbled recycled tire rubber materials are also used in-place of aggregate particles but it is not very common.

Advantages

Chip sealing equipment is common in most areas. The roadway can be opened to low speed traffic just after the application of the aggregate.

Disadvantages

Chip sealing requires constant attention and frequent adjustment of application rates of aggregate, and especially asphalt, to minimize chip loss, fly rock, bleeding, and other problems. Making these adjustments takes considerable experience and knowledge. Windshields can be damaged by the loose aggregate before the excess is removed and dust is created during the brooming of the loose aggregate.

Equipment

A distributor truck dispenses the asphalt emulsion, asphalt cement, or cutback asphalt, a rock spreader applies the aggregate, a pneumatic roller reorients or seats the aggregate particles, and a mechanical broom removes the excess aggregate.

Application

Emulsified asphalt is applied from 1.36 to 2.26 liters/square meter (0.30 to 0.50 gallons/square yard). The type and size of the aggregate particles vary but usually they are between 9.5 millimeters to 12.7 millimeters (3/8 to 1/2 inch) in size and are uniformly graded and free of fines. The aggregate is applied at 14 to 27 kilograms/square meter (25 to 50 pounds/square yard).

Cost & life expectancy

A typical cost for a chip seal is \$1.44/square meter (\$1.20/square yard). The expected life of a chip seal is 4 to 6 years.

Multiple Chip Seals

Often more than one layer of a chip seal treatment is applied to a roadway. Two or three applications can be applied using the same equipment as a single chip seal treatment, see figure 7. When multiple layers are applied, the size of aggregate used in the first treatment is larger than the succeeding layers. Multiple chip seals are used to build up a thicker seal coat over an asphalt pavement, a primed base course, or used over a cement-treated base. The number of additional layers would determine the cost of the treatment as well as the life expectancy.



Figure 7—Chip seal treatment. (Photo courtesy of Asphalt Institute.)

Slurry Seal

A slurry seal is a mixture of quick setting asphalt emulsion, fine aggregate, mineral filler, additive, and water. The ingredients are carefully measured and combined on the project site and spread with a squeegee device. In small areas and parking lots, a hand squeegee is commonly used to spread the mixture. Typically a specially designed vehicle as shown in figure 8 mixes the ingredients and spreads the slurry. The vehicle has a spreader box towed behind that spreads slurry in a uniform layer. There are three common sizes of slurry seal mixtures. The three mixtures are Type III (3/8-inch minus), Type II (1/4-inch minus), and Type I (1/8-inch minus). Generally, Type I slurry seals are used in parking lots where Type II and III seals are used on streets and higher traffic roads.

Slurry seals will fill small surface cracks, stop raveling, and improve the skid resistance of the pavement.

Advantages

The surface of a slurry seal treatment is smoother than a chip seal treatment. The slurry seal treatment is therefore, more “surface friendly” than

a chip seal treatment in areas such as campgrounds. A person is able to rollerblade on a slurry seal treatment.

Disadvantages

Equipment to apply a slurry seal is not as common as the equipment for a chip seal application. Many counties, which are partners with the U.S. Department of Agriculture, Forest Service, as well as local contractors own equipment for chip seal applications but not slurry seal equipment.

Equipment

Mixing equipment is needed on the site to accurately combine the components. For all road applications a special slurry truck is needed to mix and apply the slurry.

Application

The slurry mix is applied at the thickness of the largest aggregate in the mix. The amount of aggregate, filler, additives, and water is based on the mix design depending on the component materials, environmental conditions, and existing road surface.



Figure 8—Slurry seal application. (Photo courtesy of Asphalt Institute.)

Cost and life expectancy

The typical cost is \$1.44/square meter (\$1.20/square yard). The life expectancy is 4 to 6 years.

Cape Seal

A cape seal is an application of a chip seal followed by a slurry seal. The term “cape” is derived from Cape Province of South Africa where this process was developed.

A chip seal is applied to the road then the excess aggregate is removed after the asphalt has cured. The slurry is then applied over the chip seal treatment. The Willamette National Forest in Oregon applied a cape seal in 1997 to evaluate the effectiveness of this treatment. The slurry seal was applied over a cement treated base.

Advantages

The cape seal increases the life of a chip seal by enhanced binding of the chips and protecting the surface. The cape seal surface does not have any loose aggregate and creates a dense mat.

Disadvantages

Equipment for both the chip seal treatment and the slurry seal application is required. The construction

process is longer than either a chip seal treatment or a slurry seal application.

Equipment

The asphalt distributor truck dispenses the asphalt emulsion, an aggregate spreader vehicle is required, a pneumatic roller, shown in figure 9 is used, and a broom removes the excess chips. A slurry mixer and dispensing vehicle is needed to apply the slurry.

Application

The application is the same as the chip and the slurry seals stated earlier.

Cost and life expectancy

The typical cost is \$2.39/square meter (\$2.00/square yard) with a life expectancy of 6 to 8 years.

Microsurfacing

Microsurfacing, shown in figure 10, is similar to a slurry seal type operation but allows a thicker layer to be placed (10 to 15 millimeters thick) (0.4 to 0.6-inch thick) and it cures faster than a slurry seal. Microsurfacing uses a polymer modified emulsion mixed with crushed aggregate, mineral filler



Figure 9—Pneumatic roller. (Photo courtesy of Asphalt Institute.)



Figure 10—Microsurfacing operation. (Photo courtesy of Asphalt Institute.)

(cement, lime, limestone dust, flyash), water, and additives. The additives influence the mix time and set time.

Advantages

Microsurfacing can be placed in a thicker layer than a slurry seal and, therefore, can be used to fill wheel ruts and correct minor leveling problems. It has a quicker cure time so traffic can be allowed on the road sooner than a slurry seal. It is a cold system with a temperature limitation of 10 °C (50 °F) and rising. This allows many microsurfacing operations to be done at night.

Disadvantages

Microsurfacing requires special equipment that is heavier and sturdier than a slurry machine. The cost is higher than a slurry or chip seal treatment.

Equipment

A special microsurfacing self-propelled machine is used.

Application

The microsurfacing mix is applied up to 15 millimeters (0.6 inch) in depth. Wheel ruts up to 38.1 millimeters (1.5 inch) in depth can be filled with a single pass. The amount of each material used is determined by the mix design.

Cost and life expectancy

The typical cost is \$1.79/square meter (\$1.50/square yard). The life expectancy is 6 to 8 years.

Pavement Dressing

Pavement dressings are emulsions made from asphalt, coal tar, or a combination of both. They may include rejuvenators and a variety of fillers such as fibers and mineral fillers. Polymer modified asphalt emulsions are also used in some of the

pavement dressings. Pavement dressings are used for, but are not limited to, campgrounds, administrative sites, parking lots and driveways. The pavement dressings containing coal tar are used where protection from petroleum spills are needed. This material is sprayed or squeegeed onto the pavement.

The pavement dressings fill small cracks, and seal and protect the asphalt pavement from oxidation and deterioration.

Advantages

Pavement dressings can be applied in small quantities such as on a driveway or walkway and do not require special equipment. The treated surface is smooth similar to a slurry seal.

Disadvantages

Pavement dressings are not cost effective on roadways when compared with other surface treatments.

Cost & life expectancy

The typical cost is \$0.90/square meter (\$0.75/square yard). The life expectancy is 4 to 6 years.

SUMMARY

This publication identified asphalt seal coat treatments commonly used today. The road manager still must determine the appropriate treatment based on variables unique to the road such as the road condition, climate, traffic level, time of year applying the treatment, availability of materials, availability of funds, cost of treatment, life expectancy of treatment, and other factors. The road manager should consult the geotechnical engineer to jointly determine the most cost-effective seal coat treatment, which may not be the least expensive alternative.

APPENDICES

Appendix A

Asphalt Pavement Distresses

A survey of the pavement must be conducted before a treatment can be determined. There are many types of distresses, and the severity of each will vary. The same pavement normally has a combination of distresses. Some pavement distresses are described with a possible surface treatment suggested. Table A1 at the end of this appendix summarizes these surface treatments.

Raveling and Surface Wear

Raveling is the loss of aggregate particles on the pavement surface. This could be caused by the loss of the binding properties of the asphalt in the mix due to oxidation and or asphalt stripping. When these two problems occur, vehicle tires can wear wheel paths by raveling off coarse aggregate. Wear is usually caused by studded tires, traction chains, or snow plows.

Severity	Description
Low	The pavement is slightly rough.
Medium	The pavement is moderately rough.
High	The pavement is very rough and deeply pitted.

Treatment

Any of the asphalt seal coat treatments could improve a pavement with raveling problems. For low severity raveling, a fog seal could treat the problem while a chip seal or slurry seal would be needed for medium to high severity raveling. A rejuvenating treatment may also restore the binding properties of an aged pavement surface. Surface wear problems are normally solved by chip or slurry seals.

Rutting

Rutting is a depression in the surface of the asphalt pavement caused by the deformation of the asphalt mix within the vehicle wheel path. The deformation could also be caused by the deformation of the subgrade under the pavement. When the rutting is severe, the edges of the rutted area may be elevated. If the rutting is caused by the movement in the subgrade or an unstable mix, a surface treatment will not fix the problem.

Severity	Depth of rut
Low	6.4 to 12.7 mm (1/4 to 1/2 in.)
Medium	12.7 to 19.1 mm (1/2 to 3/4 in.)
High	over 19.1 mm (over 3/4 in.)

Treatment

Microsurfacing has been used to fill ruts that are low to medium in severity. The most common method for eliminating wheel ruts is an asphalt mix overlay. If ruts are severe and the traffic volume is high, removal and replacement of the pavement may be the only successful long term solution.

Cracking

Cracks are a separation of the pavement and are categorized by the alignment of the cracks in relation to the road centerline. The width of the crack opening will vary because of the expansion and contraction of the pavement, degree of pavement oxidation, traffic volume, frost heave, etc. Some cracks exhibit much more movement than others. Cracks are wider in the winter when the pavement is cold.

Longitudinal Cracking—Cracks that are parallel to the centerline of the roadway are longitudinal cracks. These cracks tend not to exhibit as much movement as transverse cracks; therefore they are considered nonworking cracks as determined by the Strategic Highway Research Program study. If the longitudinal cracks are located in the wheel tracks, they must be treated to prevent alligator cracking.

Transverse Cracking—Cracks that are perpendicular to the centerline of the roadway are transverse cracks. These cracks are most likely caused by the shrinkage of the pavement. The longer the distance between the transverse cracks, the more lateral movement the crack will exhibit. As with any type of cracks in the pavement, the width of the opening will vary because of the expansion and contraction of the pavement. The cracks are wider in the winter when the pavement is cold.

Block Cracking—Block cracking is a series of cracks that form block shaped patterns. These rectangular shapes vary in sizes from 0.3 meter (1 foot) square to 3 meter (10 feet) squares. These can be caused by subgrade settlements, age hardening, or oxidation of the asphalt. In northern climates, these are often caused by frost heaves.

Alligator Cracking—Alligator cracks are associated with vehicle loading and, therefore, tend to appear within the wheel tracks. These cracks begin as longitudinal cracks, and the damaged area progressively increases in time if not treated. The cracks interconnect and form a pattern similar to the skin of an alligator. Alligator cracks are normally associated with pavement structural failure.

Severity	Width of crack opening
Low	Less than 6.4 mm (1/4 in.) wide.
Medium	Greater than 6.4 mm (1/4 in.) wide with no spalling on the edges.
High	The cracks are spalled on the edges and there may be several adjacent cracks.

Treatment

Crack sealing or filling is the most common method to prevent water or incompressibles from entering the cracks with low to medium severity. Sand seals, chip seals, or scrub seals may also treat the cracks of low to medium severity. Cracks that are numerous and spalled on the edges may require skin patching with fabric or rehabilitation.

Flushing

Flushing or bleeding is the result of the excess asphalt moving upwards in the pavement causing a bituminous film on the pavement surface. This could be caused by an improper asphalt concrete mix, or an improperly applied seal coat application. The visible sign of flushing is a shiny pavement surface. Flushing can be dangerous because it reduces skid resistance of vehicles, especially when the pavement surface is wet.

Severity	Within the affected area
Low	Some of the surface aggregates have been covered by asphalt.
Medium	Significant amount of the surface aggregate has been covered by asphalt.
High	Most of the aggregate has been covered by asphalt.

Treatment

For low to medium severity of flushing the simplest treatment is to apply sand over the affected area to act as a blotter for the excess asphalt. For medium to high severity a pavement milling machine is used to remove the excess asphalt. Using a high float emulsion with a chip seal may also prevent flushing.

Polished Aggregate

This occurs when the top surface of the aggregate particles is polished smooth. The surface becomes very slippery when wet.

Severity	Within the affected area
Low	A small portion of the surface aggregate has been polished smooth.
Medium	Significant amount of the surface aggregate has been polished smooth.
High	Most of the aggregate has been polished smooth.

Treatment

For all severity of polished aggregate, the surface requires a skid resistant treatment. Surface treatments including sand seals, chip seals, or slurry seals can be applied over the affected area.

Table A1—Possible treatments for distresses and typical cost and life expectancy of treatment.

	Fog Seal	Sand Seal	Scrub Seal	Chip Seal	Multiple Chip Seal	Slurry Seal	Cape Seal	Microsurfacing	Pavement Dressing
Possible Treatment for:									
Raveling & Wear	X	X	X	X	X	X	X	X	X
Rutting								X	
Cracking		X	X	X	X	X			
Flushing				X	X				
Polished Aggregate		X	X	X	X	X	X	X	X
Typical Cost (\$/sq yard)	\$0.45/sq yard	\$0.70/sq yard	\$1.30/sq yard	\$1.20/sq yard	Depends	\$1.20/sq yard	\$2.00/sq yard	\$1.50/sq yard	\$0.75/sq yard
Typical Cost (\$/sq/meter)	\$0.54/sq meter	\$0.84/sq meter	\$1.55/sq meter	\$1.44/sq meter	on number	\$1.44/sq meter	\$2.39/sq meter	\$1.79/sq meter	\$0.90/sq meter
Life Expectancy	1 to 3 years	3 to 4 years	4 to 6 years	4 to 6 years	of layers	4 to 6 years	6 to 8 years	6 to 8 years	4 to 6 years

Appendix B

Bibliography

- Asphalt Emulsion Manufacturers Association. A Basic Asphalt Emulsion Manual. Second Edition. Annapolis, Maryland.
- Asphalt Emulsion Manufacturers Association. Asphalt Emulsion. Manual Series No. 19, Third Edition. Annapolis, Maryland. Asphalt Institute. Lexington, Kentucky.
- Asphalt Institute. Asphalt in Pavement Maintenance. Manual Series No.16, Third Edition, Lexington, Kentucky.
- Hunt, Elizabeth. 1991. Asphalt Pavement Maintenance and Rehabilitation Selection Guide. June. Oregon State University. Corvallis, Oregon.
- Institute of Transportation Studies. 1984. Pavement Maintenance and Rehabilitation: Techniques Using Asphalt, University of California. Berkeley, California.
- Maupin, G.W. Jr., and C.W. Payne. 1995 Evaluation of Modified Single Seal Surface Treatments. Report No. VTRC 95-R23. May. Virginia Transportation Research Council. Charlottesville, Virginia.
- Moulthrop, James S., P.E., R. Gary Hicks, Ph.D., P.E., and Jerry Daleiden, P.E. 1998 Selecting a Flexible Pavement Maintenance Treatment, paper presented at the Western Pavement Maintenance Forum. January 26. Sacramento, California.
- Puzinauskas, V. P., and L.W. Corbett. 1978. Differences Between Petroleum Asphalt, Coal-Tar Pitch and Road Tar. Research Report 78-1. Asphalt Institute. Lexington, Kentucky.
- Wyckoff, Coleman P. 1997. Asphalt Seal Coats. June. Northwest Technology Transfer Center, Washington State Department of Transportation. Olympia, Washington.

Appendix C

Additional Sources of Information

Suppliers

Lightweight Aggregate

Expanded Shale, Clay and Slate Institute
2225 Murray-Holladay Road
Suite 102
Salt Lake City, UT 84117
(801) 272-7070

Scrub Seal

Western Emulsions, Inc.
382 E. Live Oak
Irwindale, CA 91706
(818) 358-8049

Golden Bear Products
Witco Corporation
P.O. Box 456
Chandler, AZ 85244-0161
(602) 963-2267

Organizations

Strategic Highway Research Program (SHRP)
U.S. Department of Transportation, Federal Highway Administration
Information Clearinghouse
<http://209.48.224.225:80/shrp/>

U.S. Department of Transportation, Federal Highway Administration
Office of Technology Applications
400 7th St. SW
Washington, DC 20590
<http://www.fhwa.dot.gov>

Local Technical Assistance Program (LTAP)
American Public Works Association
1301 Pennsylvania Avenue, NW
Suite 501
Washington, D.C. 20004-1701
(202) 347-7267
<http://www.ltapt2.org>

Transportation Research Board
<http://www.nas.edu/trb/>

National Technical Information Service
U.S. Department of Commerce
Springfield, VA 22161
(703) 605-6000
<http://www.ntis.gov/>

American Association of State Highway and Transportation Officials (AASHTO)
444 North Capitol Street, NW
Suite 249
Washington, D.C. 20001
(202) 624-5800
<http://aashto.org>

Asphalt Institute
P.O. Box 14052
Lexington, KY 40512-4052
(606) 288-4960
<http://www.asphaltinstitute.org/>

National Association of County Engineers
440 First Street, NW
Washington, D.C. 20001-2028
(202) 393-5041
<http://www.naco.org/affils/nace>